

Digital Image Correlation Investigations on the Interface Failure of a Sandwich Composite

Matei Constantin Miron, Dan Mihai Constantinescu

Universitatea POLITEHNICA București, Splaiul Independenței nr. 313, București
e-mail: dan.constantinescu@upb.ro

Abstract

Interface damage characterization and interlaminar failure of sandwich specimens with one initial interlaminar delamination is done by using the digital image correlation method. Mode I tests reveal interesting particularities on damage localization and strain variation when damage is finalized. After analyzing the experimentally obtained results, we make comments on the four characteristic domains which describe the opening strains in the interface and in the core. The crack opening can be also measured when damage is finalized and crack grows further on. Such an approach gives a deeper insight on the interface phenomena which are essentially nonlinear.

Key words: sandwich composite, interlaminar failure, digital image correlation, crack propagation

Delamination problem – challenges and progress

The laminated and sandwich material concept has a huge potential but needs to avoid structural collapse in a composite which is often caused by the evolution of different types of damages created in a local zone of the structure. The particular damage modes depend upon loading, lay-up and stacking sequence. One should be able to understand and control for a laminated or sandwich composite material its lay-ups for special orthotropy, the laminate design, strain and stress analysis, stiffness, failure characterization – failure modes and analysis, failure criteria, edge delamination problems.

The fracture behaviour of high performance composite laminates is a complex issue, involving both intralaminar damage mechanisms (e.g. matrix cracking, fibre breaking) and interlaminar damage (delamination). Some progress has been made lately in the development of analytical tools for the prediction of intralaminar damage growth, but similar tools for delamination characterisation are still not available. Without a better understanding of progressive failure, the fracture criteria and predictive capabilities will be limited. Delamination is one of the predominant forms of failure in laminated composites due to the lack of reinforcement in the thickness direction. The analysis of delamination is commonly divided into the study of initiation and the monitoring of the propagation of an already initiated defect. Crack propagation is usually predicted using the Fracture Mechanics approach which eliminates the difficulties associated with the stress singularity at the crack front, but requires the presence of a pre-existing delamination whose exact location may be difficult to determine in real applications. It is also essential to develop computational methods for the simulation of the delamination growth and the interlaminar damage mechanisms. In order to do this it is important to carefully observe and understand the fracture processes to be simulated.

The purpose of this research is to characterize damage and delamination in sandwich specimens with a rigid core (polyurethane foam), to observe the interlaminar damages and failures, and to try to understand most of the local processes. We continue the using of digital image correlation (DIC) for establishing the three-dimensional displacements of the tested composites and for monitoring the crack propagation [1,2]. Clearly phenomena are non-linear, and the use of LEFM and the concept of the critical energy release rate is doubtful. The use of digital correlation method gave new perspectives in the evaluation of local parameters suitable for damage characterization and interlaminar failure. We proposed as a failure parameter the local strain at the crack tip established exactly before the stable crack propagation, which was in our tests 17.5 % (mean value). Of course that such a parameter is specimen and loading dependent, but, however, it can be established for each situation. An alternative parameter can be the crack tip opening displacement (CTOD) which has an average value of 0.24 mm, when unstable crack propagation occurs. Further developments were obtained by using numerical simulations and cohesive finite elements.


Present work concentrates on the issue of interface failure in a sandwich component with a glass fibre skin and a rigid polyurethane core. Digital image correlation is used in monitoring the evolution of failure from an initial interface crack by using two rows of virtually emulated strain gages of 1.4 mm at the interface and beneath the interface. Their number for each test depends on the way in which the crack propagated. In this way many information on strain evolution and localization are acquired.

Theoretical formulation of the interface crack problem

A crack at the common interface or parallel to the interface of two materials with different elastic constants can be encountered in many practical situations, therefore establishing the stress and strain fields around the crack tip as well as the propagation of the crack are of real interest. The interface by itself can have a high toughness, which complicates the occurring problems. If the interface between the two different media is of low toughness crack propagation will be produced in a mixed mode and not in mode I, as it happens in homogeneous and isotropic body. The asymmetry of the moduli of elasticity and the possible unsymmetrical loading will lead to the existence of mode II. Complicated local mechanisms may appear, in between the propagation of the crack along the interface and the deviation of its path through a rapid change of direction, different behaviours being given by the relative toughnesses of the two materials in contact. The classical mathematical formulations of these problems were established as follows. Williams [3], Sih and Rice [4], Rice and Sih [5] use functions of complex variable and series expansions, and Erdogan [6,7] solves the problem with the help of Hilbert spaces. Bahar [8] introduces a technique of integral transformations. Williams [3] has the merit of first showing the oscillatory character of the stresses proportional to $r^{-1/2}(\sin)$ or (\cos) of the argument $(\varepsilon \log r)$, where r is the distance measured from the crack tip and ε depends on the elastic constants of the materials. His solution hasn't defined quantitatively the stress fields, but has presented qualitatively the problems which appear. Bahar [9] showed that the stresses don't have an oscillatory character and his solution is questionable. We have to underline some of the papers written by Hutchinson and co-workers [9,10,11] which not only brought significant clarifications of the problems, but also studied in detail the case of the cracks parallel to the interface. This problem was also discussed in [12].

Two linear elastic and isotropic materials are divided by an interface and a crack along it (Fig. 1). The materials are #1 (top) and #2 (bottom) having at the crack tip a cartesian (x,y) system or a polar one (r, θ) with different elastic constants $G_i, E_i, \nu_i, (i = 1,2)$ as: transversal modulus of elasticity, longitudinal modulus of elasticity, respectively Poisson's ratio. It is to be notated $k_i = 3 - 4\nu_i$ for state of plane strain and $k_i = (3 - \nu_i)/(1 + \nu_i)$ for state of plane stress.

Dundurs [13] showed that in the presence of two different materials there are two important parameters which depend on the elastic constants are to be calculated as :

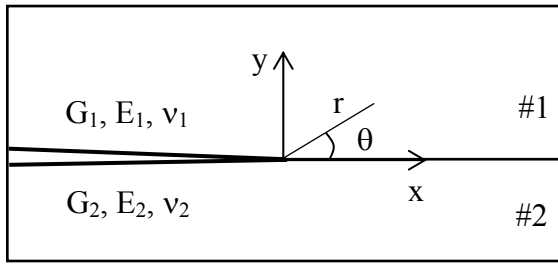

$$\alpha = \frac{G_1(k_2 + 1) - G_2(k_1 + 1)}{G_1(k_2 + 1) + G_2(k_1 + 1)} \quad \text{and}$$

$$\beta = \frac{G_1(k_2 - 1) - G_2(k_1 - 1)}{G_1(k_2 + 1) + G_2(k_1 + 1)}. \quad (1)$$

A more suggestive form for α is

$$\alpha = (\bar{E}_1 - \bar{E}_2) / (\bar{E}_1 + \bar{E}_2) \quad (2)$$

Fig. 1. Notation of the interface constants

where $\bar{E}_i = E_i / (1 - \nu_i^2)$ for plane strain and $\bar{E}_i = E_i$ for plane stress. Parameters α and β become zero if it is only one material. The value of the parameter α reaches +1 if material #1 is more rigid than material #2, and -1 when material #1 is more deformable (compliant) than #2.

For plane strain the parameter β becomes zero when both materials are incompressible ($\nu_1 = \nu_2 = 0,5$). For plane stress, $\beta = \alpha/3$ when $\nu_1 = \nu_2 = 1/3$. When $\nu_1 = \nu_2$ parameter α is the same for plane stress or plane strain.

The difference between the elastic constants of the two materials produces an oscillatory stress field [3], proportional to the trigonometric functions (sin) or (cos) of the form $\sigma \sim (\sin, \cos)(\varepsilon \log r)$, with r being notated the radius measured from the crack tip till the considered point, and ε is a so-called oscillatory index defined as

$$\varepsilon = \frac{1}{2\pi} \ln \left(\frac{G_1 + k_1 G_2}{k_2 G_1 + G_2} \right) = \frac{1}{2\pi} \ln \left(\frac{1 - \beta}{1 + \beta} \right). \quad (3)$$

At the tip of the interface crack in between two semi-spaces will result a complex stress intensity factor $K = K_1 + iK_2$ with a real part K_1 (measure of the singularity of the normal stresses) and an imaginary part K_2 (connected to the singularity of the shearing stresses), being connected to the conventional values belonging to mode I and mode II.

The relations which calculate the stresses become complicated, but for $r \rightarrow 0$ and $\theta = 0$ they simplify as in [9] and the relation results

$$\sigma_y + i\tau_{xy} \rightarrow \frac{K r^{i\varepsilon}}{\sqrt{2\pi r}} \quad (4)$$

with $r^{i\varepsilon} = \cos(\varepsilon \ln r) + i \sin(\varepsilon \ln r)$. All these lead to a so-called *oscillatory singularity* of the stresses which does not appear in LEFM. The singular stress fields ahead the interface crack are given by the relations:

$$\sigma_y = \text{Re}[K r^{i\varepsilon}] (2\pi r)^{-1/2}, \quad \tau_{xy} = \text{Im}[K r^{i\varepsilon}] (2\pi r)^{-1/2}. \quad (5)$$

If a crack of length $2a$ is located at the interface of two semi-infinite materials loaded by σ_y^∞ and τ_{xy}^∞ , then at the right tip of the crack it is to be obtained

$$K_1 + iK_2 = (\sigma_y^\infty + i\tau_{xy}^\infty) (1 + 2i\varepsilon) (\pi a)^{1/2} (2a)^{-i\varepsilon}. \quad (6)$$

These stress intensity factors (SIFs) will be influenced by the dimensions of the studied body, the interaction between the crack and the loading, as well as the interaction between the crack and the boundary of the body.

Tensile testing of the skin and core

All presented tests were reported by Miron in [14]. The tested sandwich composite has skins made from mat with a density of 300 g/m^2 and a core with density of 200 kg/m^3 . The skins and the core are glued together by a bicomponent polyurethane adhesive. Traction testing of both skin and core are done on a LLOYD LRX PLUS testing machine with the NEXYGEN software at a speed of loading of 3 mm/min . An extensometer Epsilon with a gage of 50 mm was also used to measure strains. On the other hand digital image correlation (DIC) with the ARAMIS 2M system were used to monitor strains on the tested specimens. A calibre of $25 \times 38 \text{ mm}$ was used. One frame per second was acquired.

Testing of the skin

Specimens of about 20 mm width and 1.5 mm thickness were tested. Five tests were done and each time, in order to calculate also Poisson's ratio, two virtual strain gages of 15 mm were emulated in the middle of the specimen: one longitudinal and the other transversal (Fig. 2). In figure 3 longitudinal strains before failure are shown in the skin as being localized around glass fibres which break. Initial failure of the mat fibres start at about 60 MPa and nonlinearities in the stress-strain diagram appear. The obtained results for the five tests are given in table 1.

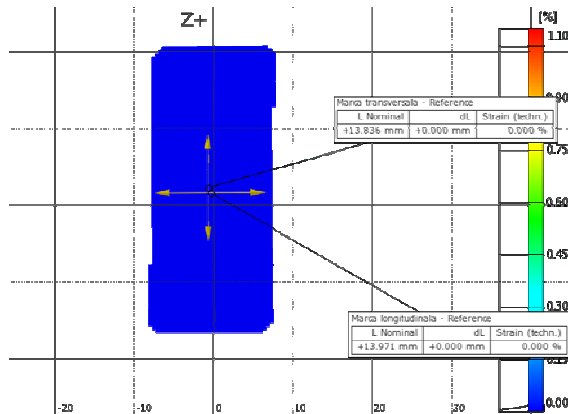


Fig. 2. Skin with virtual strain gages used in ARAMIS

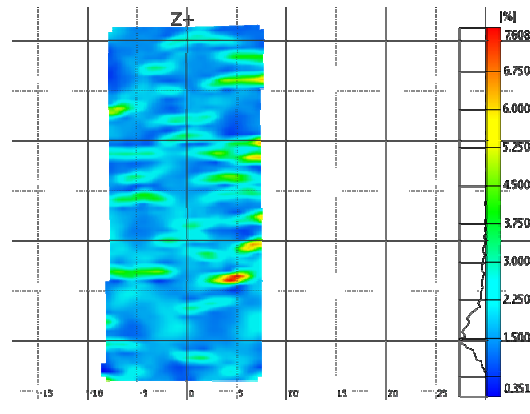


Fig. 3. Longitudinal strains in the skin before failure

Table 1. Experimental results for the traction of the glass fibre mat skin

Dimensions of specimens		Established properties			
No.	Section [mm]	Ultimate stress [MPa]	Maximum strain at failure [%]	Longitudinal modulus [MPa]	Poisson's ratio [-]
1	19.1 1.98	84.27	1.055	8743.31	0.324
2	16.9 1.65	109.62	1.417	8401.74	0.335
3	18.3 1.88	105.98	1.153	10176.47	0.339
4	18.1 1.6	92.9	1.094	9518.89	0.327
5	16.51 1.59	137.35	1.916	8173.64	0.329

For further calculations we considered, in average, maximum (ultimate) strength as 106 MPa, elongation at failure of 1.33 %, longitudinal (Young’s) modulus as 9000 MPa, and Poisson’s ratio as 0.33.

Testing of the core

Same procedure as before was used for the tensile testing of the polyurethane core with a density of 200 kg/m³. The response of the material is nonlinear and more ductile after a stress of 3.5 MPa is reached, and failure is produced around 5.9 MPa. The level of strains is quite low, and no specific indication is noticed before breaking. Just as an example for one test, the longitudinal strains are shown in the linear elastic domain at a stress of 0.9 MPa (Fig. 4), and in the last frame before failure at 5.98 MPa (Fig. 5).

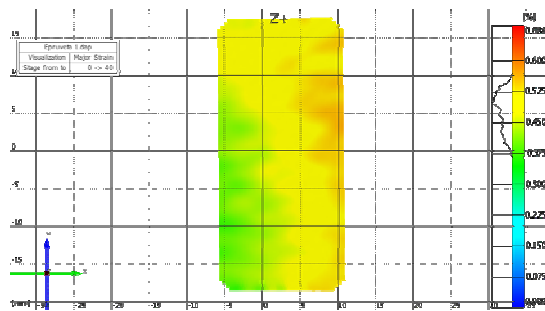


Fig. 4. Longitudinal strains at 0.9 MPa

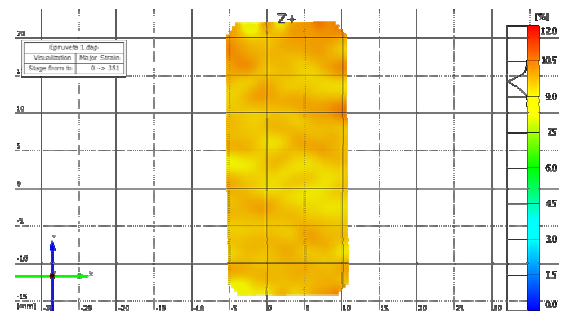


Fig. 5. Longitudinal strains at 5.98 MPa

Results of two tests are given hereby, in table 2. As seen in figure 5, before the failure of the specimen no indication of the local strain increase in a specific section was noticed.

Table 2. Experimental results for the traction of the polyurethane core with density 200 kg/m³

Dimensions of specimens			Established properties			
No.	Section [mm]		Ultimate stress [MPa]	Maximum strain at failure [%]	Longitudinal modulus [MPa]	Poisson’s ratio [-]
1	19.70	6.55	5.980	12.370	172.059	0.366
2	19.76	6.89	5.940	11.890	172.077	0.374

In average, maximum (ultimate) strength is 5.96 MPa, elongation at failure of 12.13 %, longitudinal (Young’s) modulus as 172.1 MPa, and Poisson’s ratio as 0.37.

Setup of the experiment

The sandwich has the skins with average thicknesses: top of 1.73 mm, and bottom of 1.98 mm. The polyurethane core is about 12.5 mm. An initial delamination of about 45 mm is produced by introducing a non-adherent film at one of the interfaces. In order to be able to load the specimen two special tabs of 25 mm are glued on the top and bottom of the specimen towards the end with the insert. The whole specimen is painted in white and black speckle dots in order to be able to use DIC. The specimen prepared for testing is shown in figure 6.

The testing of the sandwich specimen in mode I is done in order to establish the opening strain at the initiation of the degradation and the evolution of the opening strain during crack propagation. On the other hand, the crack opening when damage is completed before failure is produced at the interface is also monitored.



Fig. 6. Sandwich composite specimen prepared for testing

Six specimens were tested till the final failure. Length of the initial delamination is measured and the monitored points during testing are mentioned in table 3.

Table 3. Dimensions of the tested sandwich specimens and the position of the monitored points

Specimen No.	Dimensions		Monitored position					
	Width	Thickness	Length of initial delamination	Position of the monitored points				
	[mm]	[mm]		[mm]	[mm]			
1	19.8	16.9	46.92	51.98	56.88	61.97	66.91	69.39
2	20.0	16.9	47.05	52.44	59.95	77.4		
3	20.1	17.0	45.17	62.44	73.16			
4	20.3	16.5	53.36	Crack propagates once in the visual field of ARAMIS				
5	20.1	16.9	46.54	51.54	58.44	63.47	69.88	
6	20.3	16.5	43.02	49.91	63.29			

Results on the interface failure

Speed of loading is also 3 mm/min, and the same calibre 25 x 38 mm is used. Due to the asymmetric position of the interface crack in the specimen (only one interface has an initial delamination) the specimens have also a rotation while the test is completed. In some tests the crack propagated with a pop-in. If the interface crack propagates too much it may get out the monitored field by the ARAMIS system which is about the same size as the used calibre. Therefore not for all tests we obtained the same amount of data.

The analysis of local strain fields around the tip of the initial delamination and after crack propagation is done by using DIC and virtual strain gages of about 1.4 mm. They are positioned normal to the interface and the following notation is used: *I* strain gage is at the interface with

the top tip on the lower part of the skin and the bottom tip on the core; *S* strain gage is positioned beneath the *I* strain gage having its top tip common with the bottom *I*-tip and the bottom tip in a lower position in the core (Fig. 7). We are going to call: the *I* strain gage as being interface, and the *S* strain gage as being core.

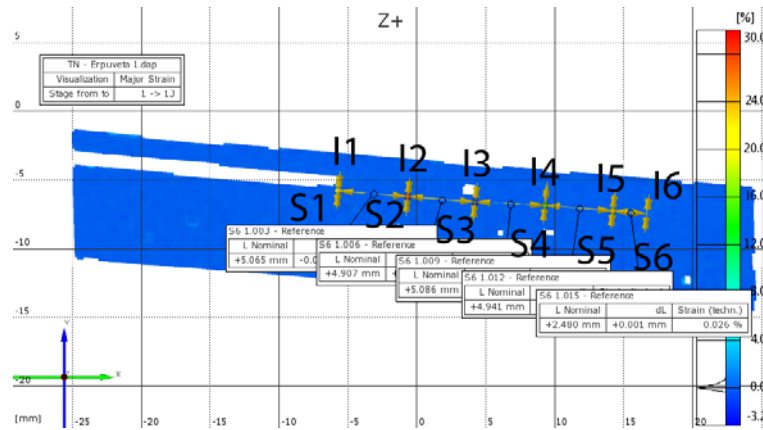


Fig. 7. Position of virtual strain gages along the interface for test 1

Strain gages *I* and *S* are in the same location for one monitored point, that is we measure the strains at the interface and in the core. For test 1 there are five positions which are monitored during the failure of the interface crack. In table 4 the initial monitored point is at the tip of the initial delamination. Only strains measured with the *I* gages are given.

The position of the monitored point indicates the distance towards the edge of the specimen. Gage length of the virtual strain gage l_0 is indicated in table 4 as the exact values of the *I* gages in that particular location; some differences appear with respect to the reference value of 1.4 mm. The frame number is also stated when the initial and final parameters of damage are established. Theoretically, one frame is taken at one second. However, it has been noticed that this is not always true, that is we cannot convert difference in the numbers of frames into time elapsed between initial and final damage.

For test 1 are shown the measurements done before and after the second crack propagation (Fig. 8). The initial and final damage parameters (show in table 4) are quantified in corresponding frames by using DIC.

The initial and final parameters of damage are given by the opening strain and relative displacement of the crack flanks – crack opening; these are measured with the locally emulated strain gage and directly with the ARAMIS system. It was tried to keep a distance of about 5 mm in between two consecutive monitored points. This was not always possible as we were interested to establish exactly the position on the specimen in which damage was finalized, that is there was no material in that location. The last analyzed point for each test was chosen as close as possible to the crack position at the end of the analysis.

The moment of damage initiation was chosen as the one at which we obtain the maximum tensile strain in the core of the sandwich, measured with virtual strain gage *S*. After attaining this maximum the material of the core relaxes, and the damage is considered as finalized. Meanwhile we measure significant local strains at the interface and failure is produced by the crack propagation. When strain in core diminishes the tip of the crack moves beyond the monitored point.

In figure 9 is presented the typical variation of strains in the interface in a monitored point which is initially further away from the tip of the initial delamination [14]. For the second crack propagation the damage processes are produced in between frames 305 and 350 (Table 4). There are four distinctive domains of strain variations which are obtained:

- *domain I* in which the interface and the core are in compression due to the loading of the specimen; meanwhile the crack propagates in a stable manner towards the monitored point;
- *domain II* in which both interface and core are loaded in tension; the tip of the crack reaches the monitored point;
- *domain III* while damage is produced with increasing strains in the interface and relaxation of strains in the core;
- *domain IV* registers the strains in the material of the core; meanwhile the crack exceeds the point of measurement and, although strains in interface still increase there is no physical significance for such a trend as there is no material left at the interface.

Table 4. Behaviour of the interface zone. Strain and opening of the crack

Test no.	Monitored point (crack tip)		Initial parameters of damage			Final parameters of damage			
	Nr.	Strain gage position	Gage length (l_0)	Frame	Strain	Crack opening (Δl)	Frame	Strain	Crack opening (Δl)
		[mm]	[mm]	[-]	[%]	[mm]	[-]	[%]	[mm]
1	1	46.92	1.40	128	8.72	0.122	208	30.28	0.432
	2	51.98	1.40	251	6.67	0.093	269	24.80	0.347
	3	56.88	1.40	305	6.55	0.092	330	28.66	0.402
	4	61.97	1.76	375	8.70	0.153	394	32.45	0.57
	5	66.91	1.40	417	5.00	0.07	458	26.00	0.364
	6	69.39	1.40	468	5.41	0.076	495	32.47	0.455
2	1	47.05	1.38	134	9.63	0.133	166	32.78	0.451
	2	52.44	1.38	176	7.06	0.097	208	32.32	0.445
	3	59.95	1.41	270	9.40	0.132	Unstable propagation; parameters cannot be established		
	4	77.4	1.41	310	10.50	0.149	488	29.48	0.415
3	1	45.17	1.41	96	11.11	0.156	148	27.50	0.387
	2	62.44	1.57	295	10.36	0.163	325	37.10	0.583
	3	73.16	1.59	401	7.12	0.113	439	24.20	0.386
4	1	53.36	1.39	154	6.70	0.093	235	18.08	0.251
5	1	46.54	1.43	111	4.60	0.0658	176	39.90	0.572
	2	51.54	1.41	179	4.69	0.0662	215	34.22	0.483
	3	58.44	1.40	264	5.91	0.083	284	16.47	0.231
	4	63.47	1.40	327	9.82	0.137	353	20.50	0.286
	5	69.88	1.38	421	13.41	0.185	427	25.17	0.348
6	1	43.02	1.43	67	8.27	0.119	151	34.17	0.49
	2	49.91	1.43	202	6.70	0.096	213	14.06	0.201
	3	63.29	1.42	304	7.34	0.104	350	32.64	0.463

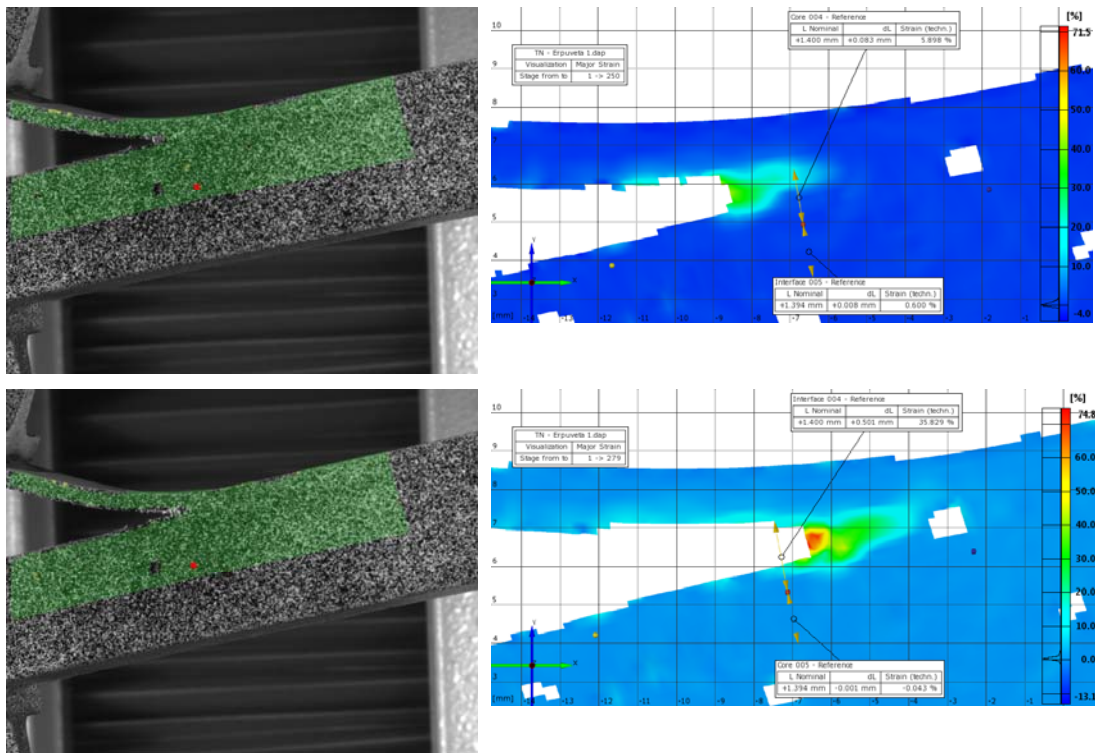


Fig. 8. Picture of the specimen from test 1 and DIC analyses before and after the second crack propagation

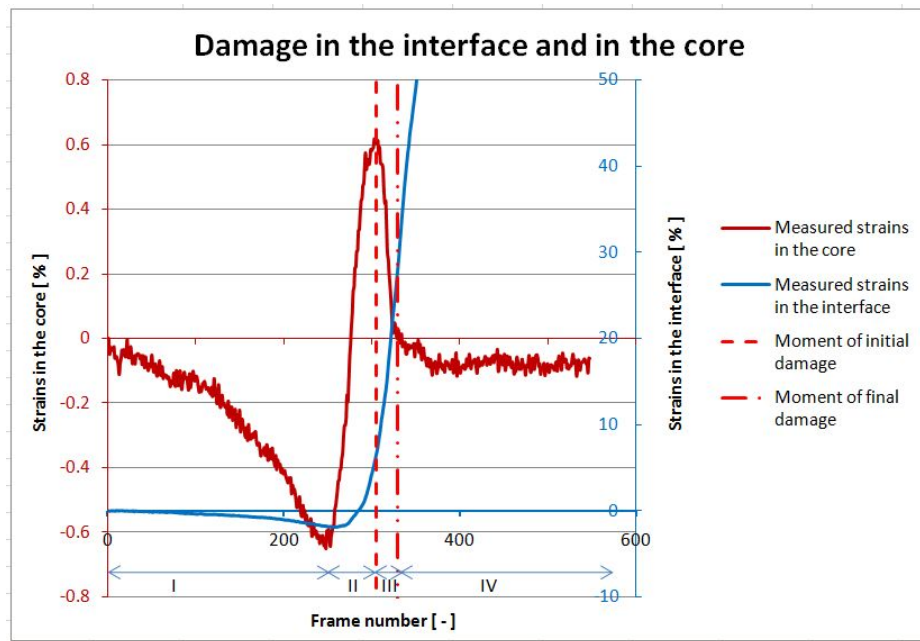


Fig. 9. Variation of strains at the interface and in the core in a monitored point while damage is produced

After the initiation of damage in the interface the material around the tip of the crack (core) relaxes and strains diminish; meanwhile strains in interface increase significantly. The final (complete) damage of the interface zone is attained when the material of the core relaxes completely and strains remain mostly constant, as seen in figure 9 (domain IV).

Comment on the interface parameters

Coming back to the calculus of interface parameters α and β established by Dundurs, in our case we can consider material #1 as being the glass fibre mat skin with $E_1 = 9000$ MPa and $\nu_1 = 0.33$, and material #2 the polyurethane core with $E_2 = 172.1$ MPa and $\nu_2 = 0.37$. State of plane stress is considered. Therefore $k_1 = 2.007$ and $k_2 = 1.9197$. By using relation (2) it results $\alpha = 0.9625$, and from (1) $\beta = 0.3028$. By using equation (3) the value of the oscillatory index becomes $\varepsilon = -0.1$. Another important interface parameter was established by Hutchinson *et al.* [9] who made an energetic equivalence between the complex generalized SIF notated $K = K_I + iK_2$, and the classical ones notated K_I and K_{II} (for modes I and II) through the relation

$$K_I^2 + K_{II}^2 = q^2 K \bar{K} \quad (7)$$

in which \bar{K} is the conjugated of the complex SIF K . In our situation $q = 0.68$.

It comes out that mode II is also present in our particular case of the interface problem for the sandwich specimen. We can evaluate for the moment - from the experimental measured displacement fields - that mode II is about 10 % out of mode I. Further analyses will elaborate on this issue.

Conclusions

The issue of interface failure in a sandwich component with a glass fiber skin and a rigid polyurethane core is analyzed by using the digital image correlation method. Virtual strain gages are emulated at the interface and beneath it, in the material of the core. The moment of damage initiation and its evolution are monitored by measuring the local opening strain with the ARAMIS system. Several monitored points assess crack propagation and the response of the skin and of the core when failure is finalized. Crack opening can be also measured when failure is completed.

Four main domains are encountered and comments in figure 9 are done concerning their characteristics. Mixed modes are present at the interface and their analyses is going to be done elsewhere. Strain localization phenomena will be discussed in more detail by enlarging the analyses on successive failures at the interface during the same test. All these phenomena are essentially nonlinear and the proposed procedure gives a more realistic perspective on the evaluation of interlaminar damage.

Acknowledgements

The research done by PhD student eng. Matei Constantin Miron has been funded by the Sectoral Operational Programme **Human Resources Development** 2007-2013 of the **Romanian Ministry of Labour, Family and Social Protection** through the Financial Agreement POSDRU/6/1.5/S/19.

References

1. Constantinescu, D.M., Miron, M.C., Apostol, D., Evaluation of interlaminar damage and crack propagation in sandwich composites, *Lucrarile celui de-al XIV-lea Simpozion International de Mecanica Ruperii, 10-11 Octombrie, Brasov, FRAM 2008*, Editura Universităţii

- Transilvania din Braşov, Editura Universităţii Petrol şi Gaze din Ploieşti, ISSN 1453-6536, p. 3-9, 2008.
2. Miron, M.C., Apostol, D.A., Constantinescu, D.M., Interactions of neighbouring delaminations in a sandwich composite, *Lucrarile celui de-al XV-lea Simpozion National de Mecanica Ruperii, Sibiu, 6 – 7 Noiembrie 2009*, Editura Universitatii Petrol – Gaze din Ploiesti, Editura Universitatii “Lucian Blaga” din Sibiu, ISSN 1453-6536, p. 1 – 8, 2009.
 3. Williams, M.L., The Stresses Around a Fault or Crack in Dissimilar Media, *Bulletin of the Seismological Society of America*, Vol. 49, pp. 199-204, 1959.
 4. Sih, G.C., Rice, J.R., The Bending of Plates of Dissimilar Materials With Cracks, *Journal of Applied Mechanics*, Vol. 31, pp. 477-482, 1964.
 5. Rice, J.R., Sih, G.C., Plane Problems of Cracks in Dissimilar Media, *Journal of Applied Mechanics*, Vol. 32, pp. 418-432, 1965.
 6. Erdogan, F., Stress Distribution in a Nonhomogeneous Elastic Plane With Cracks, *Journal of Applied Mechanics*, Vol. 30, pp. 232-236, 1963.
 7. Erdogan, F., Stress Distribution in Bonded Dissimilar Materials with Cracks, *Journal of Applied Mechanics*, Vol. 32, pp. 403-410, 1965.
 8. Bahar, L.Y., *On an Elastostatic problem in Nonhomogeneous Media Leading to Coupled Dual Integral Equations*, PhD dissertation, Lehigh University, Bethlehem, Pa., 1963.
 9. Hutchinson, J.W., Mear, M.E., Rice, J. R., Crack Paralleling an Interface Between Dissimilar Media, *Journal of Applied Mechanics*, Vol. 54, pp. 828-832, 1987.
 10. Suo, Z., Hutchinson, J.W., Interface Crack between Two Elastic layers, *International Journal of Fracture*, Vol. 43, pp. 1-8, 1990.
 11. Hutchinson, J. W., Suo, Z., Mixed Mode Cracking in Layered Materials, *Advances in Applied Mechanics*, Vol. 29, New York, Academic Press, pp. 63-91, 1992.
 12. Smith, C.W., Gloss, K.T., Constantinescu, D.M., Liu, C.T., Stress Intensity Factors for Cracks Within and Near to Bondlines in Soft Incompressible Materials, *Recent Advances in Solids and Structures - 2000*, ASME, *PVP.-Vol. 415*, pp. 1-9, 2000.
 13. Dundurs, J., *Mathematical Theory of Dislocations*, ASME, New York, 1969.
 14. Miron, M.C., *Analiza propagării fisurilor interlaminare în compozite de tip sandwich*, Master in Engineering dissertation, University POLITEHNICA of Bucharest, 2010.

Investigații ale cedării interfeței dintr-un material compozit sandwich prin metoda corelării digitale a imaginii

Rezumat

Metoda corelării digitale a imaginii este folosită pentru descrierea fenomenelor de degradare interlaminară și de cedare a zonei de interfață, specifice materialelor de tip sandwich. Testele realizate prin încărcarea în modul I a zonei de interfață oferă rezultate interesante legate de localizarea degradării și a variației deformațiilor specifice la finalizarea degradării. În urma analizei experimentale se fac observații cu privire la existența a patru domenii principale ce descriu deformațiile specifice ce iau naștere în zona de interfață și în miezul materialului. Deschiderea fisurii poate fi măsurată în momentul finalizării degradării, respectiv în momentul în care fisura se propagă. Această abordare aprofundează modul de interpretare a fenomenelor neliniare ce apar în zona de interfață.